



HAL
open science

Terpene and dextran renewable resources for the synthesis of amphiphilic biopolymers

Marie-Hélène Alvès, Jean-François Tranchant, Emilie Gombart, Gilles Sagorin, Sylvain Caillol, Laurent Billon, Maud Save

► **To cite this version:**

Marie-Hélène Alvès, Jean-François Tranchant, Emilie Gombart, Gilles Sagorin, Sylvain Caillol, et al.. Terpene and dextran renewable resources for the synthesis of amphiphilic biopolymers. *Biomacromolecules*, 2014, 15, pp.242-251. <10.1021/bm401521f>. <hal-01097130>

HAL Id: hal-01097130

<https://univ-pau.hal.science/hal-01097130v1>

Submitted on 2 Dec 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

Terpene and dextran renewable resources for the synthesis of amphiphilic biopolymers

Journal:	<i>Biomacromolecules</i>
Manuscript ID:	bm-2013-01521f.R2
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Alvès, Marie-Hélène; IPREM-Equipe de Physique et Chimie des Polymères,, CNRS - Université de Pau et des Pays de l'Adour Sfeir, Huda; IPREM-Equipe de Physique et Chimie des Polymères,, Tranchant, Jean-François; LVMH Recherche Parfums et Cosmétiques, Gombart, Emilie; LVMH Recherche Parfums et Cosmétiques, Sagorin, Gilles; DRT, Dérivés Résiniques et Terpéniques, Caillol, Sylvain; Institut Charles Gerhardt UMR CNRS 5253 Equipe Ingénierie et Architecture Macromoléculaire, ENSCM, Billon, Laurent; IPREM EPCP UMR 5254, Chemistry Save, Maud; IPREM-Equipe de Physique et Chimie des Polymères, CNRS - Université de Pau et des Pays de l'Adour

SCHOLARONE™
Manuscripts

1
2
3 **Terpene and dextran renewable resources for the synthesis of amphiphilic**
4
5 **biopolymers**
6
7
8

9
10 Marie-Hélène Alvès, † Huda Sfeir, † Jean-François Tranchant, ‡ Emilie

11
12
13 Gombart, ‡ Gilles Sagorin, ▪ Sylvain Caillol, ≡ Laurent Billon, † Maud

14
15
16 Save † *
17
18
19
20

21 † CNRS, University of Pau & Pays Adour, UMR 5254, IPREM, Equipe de Physique et
22 Chimie des Polymères, 2 avenue du Président Angot, Pau, F-64053, France
23

24 ‡ LVMH Recherche Parfums et Cosmétiques, 185 Av. de Verdun, St Jean de Braye, F-
25 45804, France
26
27

28
29 ▪ DRT, Dérivés Résiniques et Terpéniques, 30 rue Gambetta, Dax, F-40100, France
30

31
32 ≡ Institut Charles Gerhardt UMR CNRS 5253 Equipe Ingénierie et Architecture
33
34
35
36 Macromoléculaire, ENSCM, 8 rue de l'Ecole Normale, 34296 Montpellier, France
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

ABSTRACT

The present work shows the synthesis of amphiphilic polymers based on the hydrophilic dextran and the hydrophobic terpenes as renewable resources. The first step concerns the synthesis of functional terpene molecules by thiol-ene addition chemistry involving amino- or carboxylic acid thiols and dihydromyrcenol terpene. The terpene modified polysaccharides were subsequently synthesized by coupling the functional terpenes with dextran. A reductive amination step produced terpene end-modified dextran with 94 % of functionalization while the esterification step produced three terpene grafted dextrans with a number of terpene units per dextran of 1, 5 and 10. The amphiphilic renewable grafted polymers were tested as emulsifiers for the stabilization of liquid miniemulsion of terpene droplets dispersed in an aqueous phase. The average hydrodynamic diameter of the stable droplets was observed at *ca.* 330 nm.

KEYWORDS : renewable resources, polysaccharide, terpene, thiol-ene chemistry

INTRODUCTION

The fossil resources depletion is leading to a growing interest toward materials derived from sustainable resources. Polysaccharides and terpenes are two interesting classes of materials issued from renewable biomass.¹⁻⁶ Polysaccharides are mainly hydrophilic and terpenes belong to hydrocarbon-rich biomass. Terpenes are either branched or cyclic unsaturated molecules which are extracted from the resin produced by conifer trees. Terpenes are an interesting class of molecules as they can represent an alternative to fossil molecules but also to hydrocarbon-rich biomass feedstock such as oilseeds and palm oil. Different terpene molecules are distilled from either turpentine or from paper oil, a by-product of the paper-making industry. Among the first recovered products, α and β -pinene are an important


1
2
3 class of molecules which are industrially transformed into a series of valuable terpenes by
4
5 various chemical reactions. Some terpene building blocks have been used for the synthesis of
6
7 different hydrophobic polymers as recently reviewed in the literature.⁵⁻⁷ Among the examples
8
9 of terpene-based polymers,^{5-6, 8-12} the synthesis of amphiphilic polymers were limited to the
10
11 design of terpene end-modified poly(ethylene oxide) polymers by anionic ring-opening
12
13 polymerization of ethylene oxide from terpene-based initiator.^{13,14}

14
15
16 In parallel, the increasing demand of materials with high performances requires modification
17
18 of natural polymers.¹⁵ Numerous examples of polysaccharide modification through synthetic
19
20 polymer grafting *via* for instance controlled radical polymerization¹⁶ or ring opening
21
22 polymerization¹⁷⁻²⁰ techniques have been described in the literature. Hydrophobically
23
24 modified polysaccharides with emulsifying properties have also been synthesized through the
25
26 grafting of hydrophobic molecules coming from fossil resources.²¹⁻²⁵ In this context, the
27
28 renewable feedstock of abundantly available terpenes and polysaccharides is attractive for the
29
30 synthesis of new amphiphilic biopolymers.
31
32

33
34 To the best of our knowledge, the synthesis of amphiphilic dextrans hydrophobically modified
35
36 by terpenes has never been reported. In the present work, the synthesis of functional terpenes
37
38 by thiol-ene reactions will offer the possibility to synthesize both linear and grafted
39
40 amphiphilic biopolymers (schemes 1 and 2). It is noteworthy that there are a few examples in
41
42 the literature on the use of thiol-ene coupling involving terpenes.^{12, 26} Recently, Meier and co-
43
44 workers made use of thiol-ene chemistry to produce limonene-based polyesters by
45
46 polycondensation of difunctional modified terpenes.¹²

47
48
49 Herein, we focused our attention on a linear low molar mass dextran as model
50
51 polysaccharide, dextran being a glucose-based neutral bacterial polysaccharide. Among the
52
53 fragrant terpenic molecules, dihydromyrcenol (2,6-Dimethyloct-7-ene-2-ol, DHM) was
54
55 chosen as a non toxic terpene containing a mono-substituted vinylic function suitable for
56
57
58
59
60

applying the chosen thiol-ene addition chemistry (Scheme 1).²⁷ Dextran will be modified by either reductive amination of the chain end with amino-derivatized DHM (Scheme 1, route A) or by esterification of hydroxyl backbone with carboxylic acid derivatized DHM (Scheme 1, route B). The efficiency of the terpene grafted dextran as polymeric emulsifier will be assessed through its ability to stabilize liquid droplets of dihydromyrcenol fragrance in water. The dispersion of such molecules by a renewable biopolymer is of interest for cosmetic field.

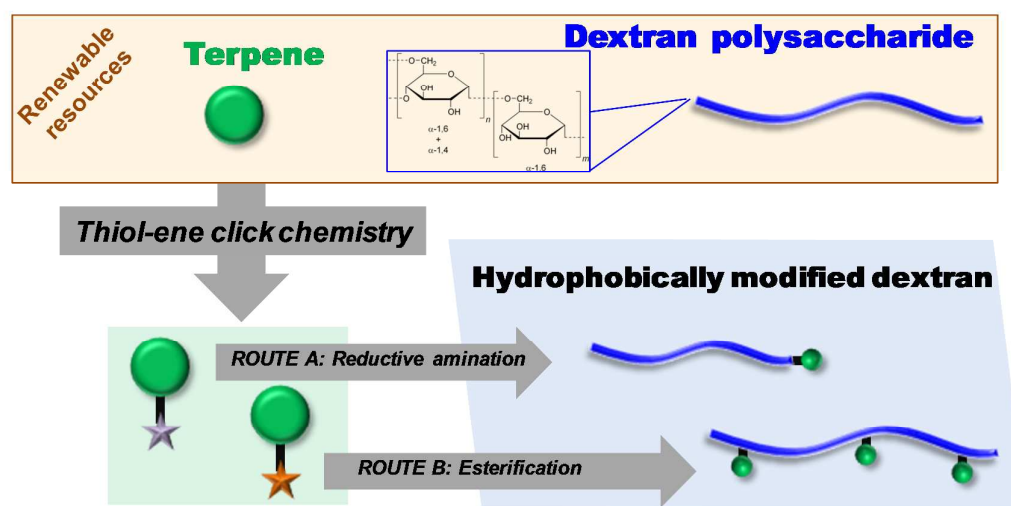

Scheme 1. Synthetic approach followed to obtain amphiphilic biopolymers

EXPERIMENTAL PART

Materials. 3-mercaptopropionic acid (Aldrich, 99 %), 2,2'-Azobis(2-methylpropionitrile) (AIBN, Aldrich 98%), 2,6-Dimethyloct-7-ene-2-ol also named dihydromyrcenol (DHM, 99.5 %), was supplied by Dérivés Résiniques Terpéniques (DRT company), cysteamine hydrochloride (Fluka, 98 %), triethylamine (Aldrich, 99 %), sodium cyanoborohydride (Aldrich, 95 %), *N,N'*-Dicyclohexylcarbodiimide (DCC, Aldrich, 99 %), hexadecane (Sigma-Aldrich, 99 %). Dimethylsulfoxide (DMSO, Technical grade, VWR) was dried over

1
2
3 molecular sieves which were previously dried under vacuum at 100 °C. Fractionated dextrans
4
5 were purchased from Serva Electrophoresis (dextran 4 and dextran 8).
6

7 **Synthesis of functional terpenes by thiol-ene addition chemistry (Scheme 2).** Terpene **1**
8
9 displayed in Scheme 2 was synthesized as follows: 2 g of DHM (1.3×10^{-2} mol), 2.9 g of
10
11 cysteamine hydrochloride (2.6×10^{-2} mol) and 105 mg of AIBN (6.4×10^{-4} mol) were mixed
12
13 in a round bottom flask sealed with a rubber septum prior degassing 15 minutes with nitrogen
14
15 flow. We should note that cysteamine hydrochloride was not initially soluble in DHM terpene
16
17 but the solubility increased during the reaction performed at 80 °C. After 24 hours of reaction,
18
19 the recovered product was an ammonium salt and the final amine (Terpene **1**) was recovered
20
21 in dichloromethane by 2 liquid-liquid extractions using a saturated sodium bicarbonate
22
23 aqueous solution. The organic phase was dried over magnesium sulfate, filtered and
24
25 evaporated to recover the pure Terpene **1** as pale yellow oil (Figure 1).
26
27

28
29 ^1H NMR (400 MHz, DMSO- d_6 , δ in ppm) 2.57 (t, 2H, $\text{NH}_2\text{-CH}_2\text{-CH}_2\text{-S}$), 2.48 (t, 2H, $\text{NH}_2\text{-}$
30
31 $\text{CH}_2\text{-CH}_2\text{-S}$), 2.45 ($\text{CH-CH}_2\text{-CH}_2\text{-S}$), 1.51 (m, 1H, $(\text{CH}_2)_2\text{-CH-CH}_3$), 1.51 (m, 1H, CH-
32
33 $\text{CHH-CH}_2\text{-S}$), 1.30 (m, 1H, $\text{CH-CHH-CH}_2\text{-S}$), 1.30 (t, 2H, $\text{HO-(CH}_3)_2\text{C-CH}_2\text{-CH}_2$), 1.25
34
35 (m, 1H, $\text{CH-CH}_2\text{-CH}_2\text{-CH}_2$), 1.07 (m, 2H, $\text{CH-CH}_2\text{-CH}_2\text{-CH}_2$), 1.05 (s, 6H, $(\text{CH}_3)_2\text{-}$
36
37 C(OH)), 0.85 (d, 3H, $\text{CH}_3\text{-CH}$).
38
39

40
41 ^{13}C NMR (100 MHz, DMSO- d_6 , δ in ppm) 69.15 (Ck), 44.35 (Ce), 41.97 (Ci), 37.39 (Cb),
42
43 37.08 (Cd'), 35.92 (Ch), 32.03 (Cc), 29.74 (Cf), 29.31 (Ca), 21.65 (Cd), 19.64 (Cg).
44

45
46 Terpene **2** displayed in Scheme 2 was synthesized as follows: 20 g of DHM (1.3×10^{-1} mol),
47
48 13.6 g of 3-mercaptopropionic acid (1.3×10^{-1} mol) and 210 mg of AIBN (1.3×10^{-3} mol)
49
50 were mixed in a round bottom flask sealed with a rubber septum prior degassing for 15
51
52 minutes with nitrogen flow. The reaction was carried out at 80 °C for 4 hours and the final
53
54 product (non colored oil, quantitative product, Figure 1) was used without purification.
55
56
57
58
59
60

¹H NMR (400 MHz, DMSO-d₆, δ in ppm) 4.07 (OH), 2.65 (t, 2H, HOOC-CH₂-CH₂-S), 2.45 (t, 2H, HOOC-CH₂-CH₂-S), 2.50 (m, 2H, CH-CH₂-CH₂-S), 1.49 (m, 1H, (CH₂)₂-CH-CH₃), 1.49 (m, 1H, CH-CHH-CH₂-S), 1.32 (m, CH-CHH-CH₂-S), 1.32 (t, HO-(CH₃)₂C-CH₂-CH₂), 1.27 (m, 2H, CH-CH₂-CH₂-CH₂), 1.07 (m, 2H, CH-CH₂-CH₂-CH₂), 1.05 (s, 6H, (CH₃)₂-C(OH)), 0.83 (d, 3H, CH₃-CH).

¹³C NMR (100 MHz, DMSO-d₆, δ in ppm) 69.08 (Ck), 43.96 (Ce), 36.82 (Cb), 36.26 (Cd'), 34.50 (Ci), 31.49 (Cc), 29.25 (Cf), 28.85 (Ca), 26.34 (Ch), 21.14 (Cd), 19.12 (Cg).

Synthesis of terpene chain end modified dextran. Dextran 4 (200 mg, $M_n = 2600 \text{ g}\cdot\text{mol}^{-1}$, $7.7 \times 10^{-5} \text{ mol}$) were mixed with 0.6 ml of distilled water. A solution of Terpene 1 (333 mg, $1.4 \times 10^{-3} \text{ mol}$) was prepared with 0.4 mL of DMSO and subsequently added into the aqueous solution of dextran 4. After 2 hours of stirring, 22 mg of sodium cyanoborohydride ($3.6 \times 10^{-4} \text{ mol}$) were added into the round bottom flask and the reaction proceeded overnight at room temperature. The initial cloudy solution became a clear, slightly yellow solution. The polymer was precipitated three times from an aqueous solution into methanol and finally dried under vacuum. The final Dext-DHM polymer is a white powder (yield 70 %).

Grafting of Terpene 2 for the synthesis of hydrophobically modified dextran. Dextran 8 (1 g, $M_n = 6600 \text{ g}\cdot\text{mol}^{-1}$, $1.5 \times 10^{-4} \text{ mol}$) were mixed with 6 mL of dried DMSO and heated at 60 °C before adding *N,N'*-Dicyclohexylcarbodiimide (3.7 g, $1.8 \times 10^{-2} \text{ mol}$). A solution of Terpene 2 (3.9 g, $1.5 \times 10^{-2} \text{ mol}$) was prepared with 2 mL of DMSO and subsequently poured into the round bottom flask containing the dextran 8 and DCC solution. The initial number of moles of DHM terpene over the number of moles of anhydroglucose units (AGU), $x = (m_{\text{DHM},0}/M_{\text{DHM}})/(m_{\text{dextran},0}/M_{\text{AGU}})$, is equal to 0.24, 1.22 and 2.44 respectively for the synthesis of Dext-*graft*-DHM₁, Dext-*graft*-DHM₅ and Dext-*graft*-DHM₁₀ grafted copolymers. After 18 hours at 60 °C, the modified dextran was precipitated three times into methanol in order to

1
2
3 eliminate free terpene. The final amphiphilic polymer was recovered as a white powder after
4
5 drying process.
6


7 **Preparation of DHM liquid miniemulsion.** Dext-*graft*-DHM₁₀ (50 mg) was mixed with 9
8
9 mL of a phosphate buffer solution (pH 8) before adding a solution containing 1 g of
10
11 dihydromyrcenol and 25 mg of hexadecane. The liquid emulsion was then subjected to high
12
13 shear pressure using a Vibra Cell 72408 ultrasonicator for 5 min at amplitude of 30% (round
14
15 bottom flask placed into an ice bath).
16

17 **Instrumentation.** Proton, carbon, and two-dimensional (COSY for COrrrelation
18
19 SpectroscopY, HSQC for heteronuclear single quantum coherence) nuclear magnetic
20
21 resonance (NMR) spectra were recorded at 25 °C on a Brüker 400 MHz spectrometer. The
22
23 average droplet diameters (D_h) were measured using a Vasco DL135 dynamic light scattering.
24
25 The number average molar mass (M_n) and dispersity (M_w/M_n) of dextran were measured by
26
27 aqueous size exclusion using the following system: 2 columns Tosoh TSK PW 2500 et TSK
28
29 PW 6000, Agilent 1260 Infinity pump, Waters 717 plus automatic injector, Multi-Angle Light
30
31 Scattering MALS Wyatt EOS (laser $\lambda = 690$ nm, cellule K5), Wyatt Optilab T-rEX
32
33 refractometer ($\lambda = 658$ nm, 25°C), ASTRA 6 software. Acetic acid 0.2 M and ammonium
34
35 acetate buffer 0.15 M was used as eluent at 0.5 mL.min⁻¹ flow rate. Samples of dextran at
36
37 concentration of 5 g.L⁻¹ were prepared and the value of refractive index increment of dextran
38
39 ($dn/dc = 0.147$) was used for molar mass calculation by MALS.
40
41
42
43
44
45
46
47

48 **RESULTS AND DISCUSSION**

49
50 **Synthesis of functional terpenes by thiol-ene coupling.** In the present work, we
51
52 started by studying the synthesis of functional terpenes by thiol-ene chemistry thermally
53
54 initiated with AIBN initiator. Two types of molecules functionalized by either a carboxylic
55
56 acid or an amino group were synthesized from the same initial dihydromyrcenol (DHM)
57
58
59
60

1
2
3 terpene with two different thiol molecules as depicted in Scheme 2. As reported in
4
5 literature,²⁷⁻²⁸ the first step of thiol-ene radical reaction is the formation of thiyl radicals (RS•)
6
7 obtained from transfer reaction of the carbon-centered radicals which are generated by the
8
9 initiator decomposition. The reaction proceeds then *via* addition of the thiyl radical through
10
11 the ene functional group to form a carbon radical. For ideal thiol-ene reactions, no
12
13 homopolymerization is observed and chain transfer of the carbon radical to another thiol
14
15 functional group follows the addition step, regenerating the thiyl radical and forming the
16
17 thiol-ene addition product (see Scheme 2). For alkyl thiols and alkenes, the reaction is chain-
18
19 transfer-limited and first order in thiol functional group concentration.²⁸⁻²⁹

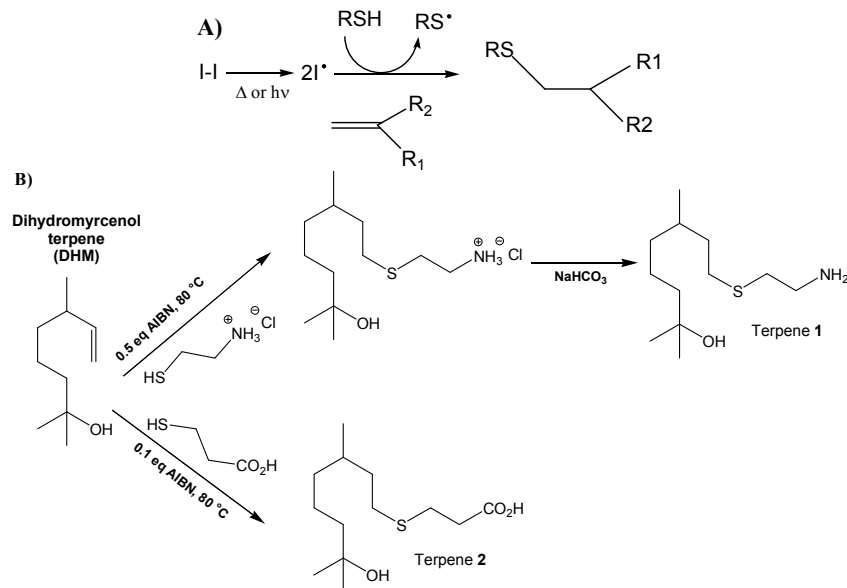

22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43 **Scheme 2.** (A) General principle of radical thiol-ene chemistry using an initiator (I-I) and a
44
45 thiol transfer agent (RSH); (B) Derivatization of dihydromyrcenol (DHM) terpene by thiol-
46
47 ene chemistry to produce functional Terpeno 1 and Terpeno 2.

48
49
50
51
52 The analysis of the proton NMR spectra of these products (Figure 1) confirmed the success of
53
54 the thiol-ene reaction performed with either cysteamine hydrochloride or 3-mercaptopropionic
55
56 acid acting as transfer agent for the coupling reaction (Scheme 2). Indeed, the disappearance
57
58
59
60

of the alkene signals of dihydromyrcenol between 4.8 and 5.6 ppm (**Figure 1**) along with the chemical shift from 2.1 ppm to 1.5 ppm of the *c* proton in α position of the alkene group (Figure 1 and Figure SI-1), proves the complete addition reaction.

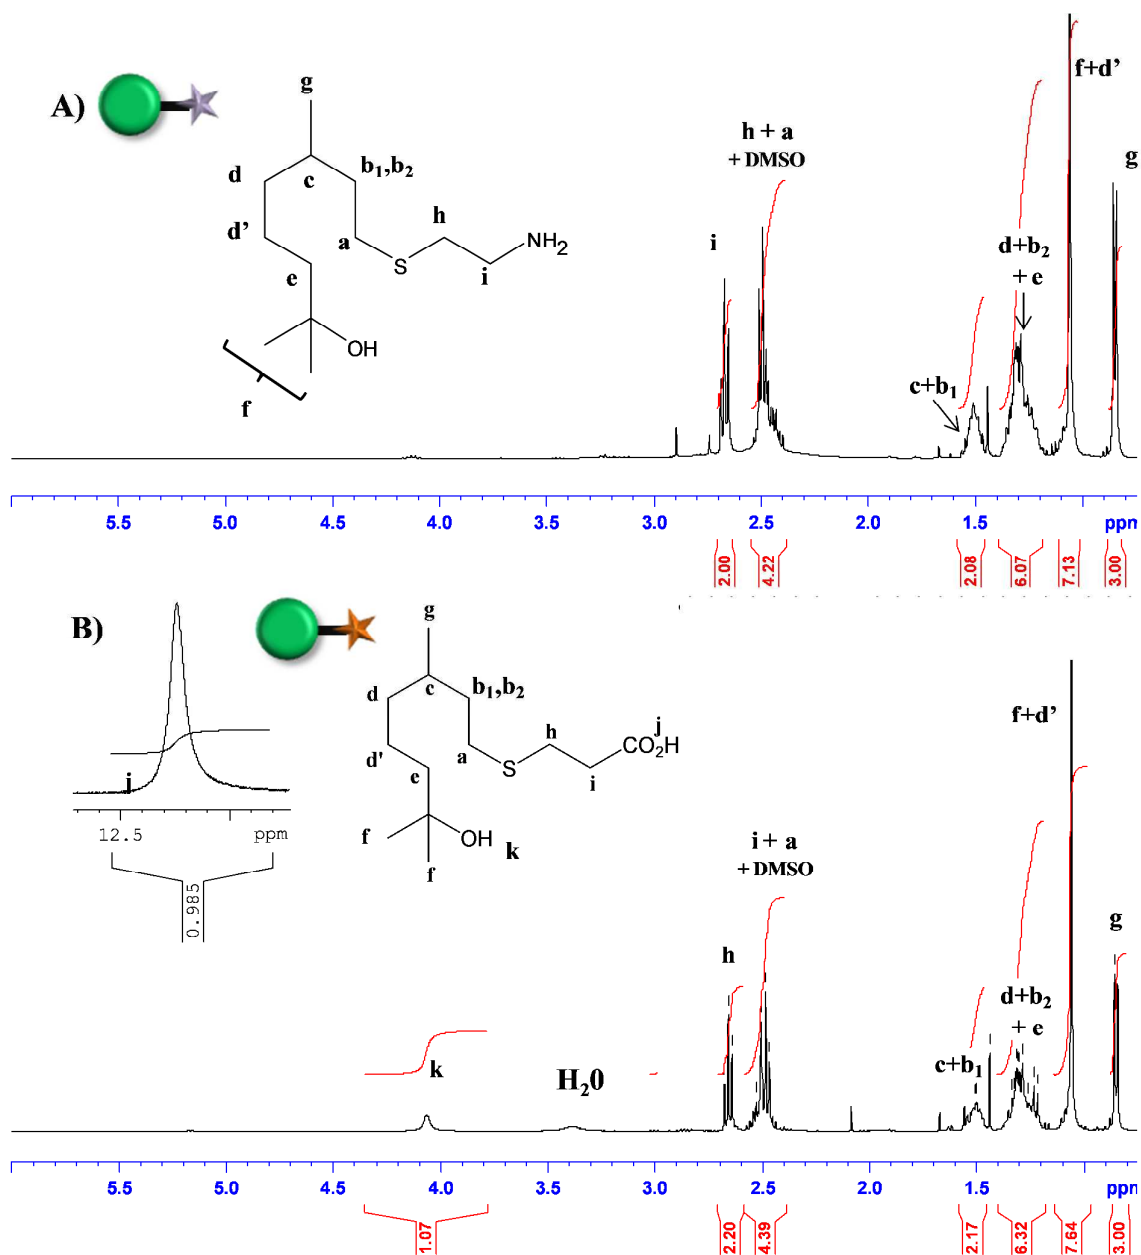
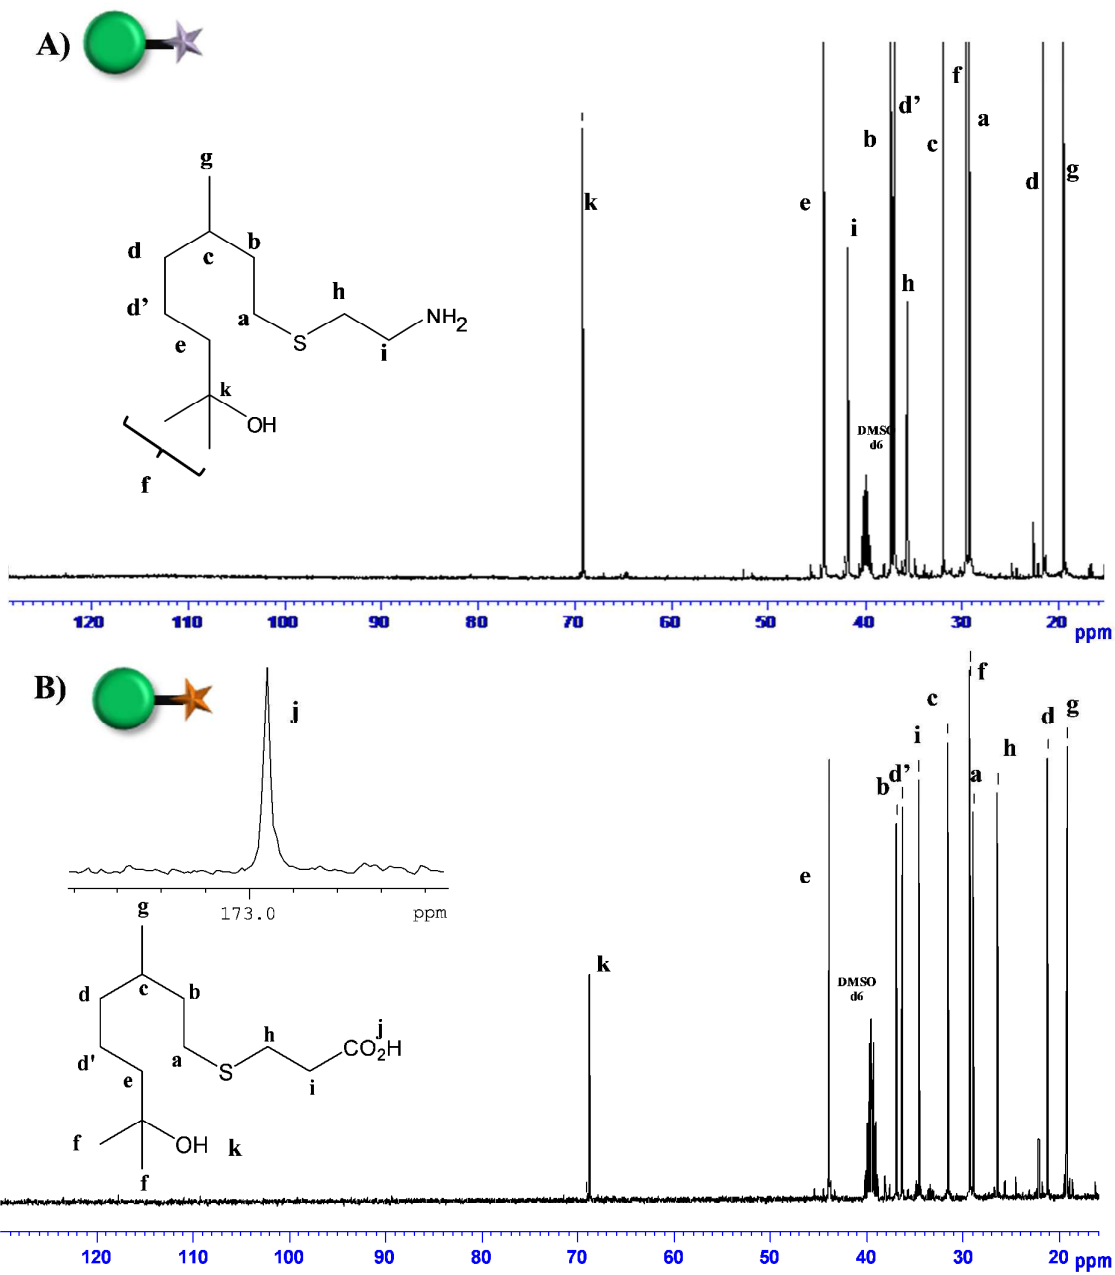


Figure 1. ^1H NMR spectra Terpene 1 (A) and Terpene 2 (B) (in $\text{DMSO-}d_6$).

For the synthesis of Terpene 1, the matching of the NMR peak integrations of terpenic moiety ($I_i = 2.00$ (2H) in Figure 1A) with the ones of the thiol moiety ($I_g = 3.00$ (3H) in Figure 1A)

1
2
3 confirms the quantitative coupling. While complete disappearance of the alkene signals
4 (Figure 1B) was also observed for the synthesis of Terpene 2 performed in stoichiometric
5 amounts of DHM and 3-mercaptopropionic acid, the NMR integrations of the thiol moiety
6 peak ($I_h = 2.20$ (2H)) exhibits 10 % excess in comparison with the NMR integration of the
7 terpene peak ($I_g = 3.00$ (3H)) (see Figure 1B). However, the good agreement between the
8 integration values of the carboxylic acid proton ($I_j = 0.985$ (1H)) and the terpenic protons ($I_g =$
9 3.00 (3H) along with the single carboxylic acid peak at 173.3 ppm were observed respectively
10 in the proton (Figure 1B) and the carbon (Figure 2B) NMR spectra of Terpene 2. These
11 observations support the absence of either residual 3-mercaptopropionic acid or oligomers
12 issued from polyesterification between the tertiary alcohol group and the carboxylic acid
13 group.
14
15
16
17
18
19
20
21
22
23
24
25
26

27 The analysis of both Terpene 1 and Terpene 2 by two dimensional heteronuclear single
28 bond correlation (HSQC) NMR (Figure 3) enabled us to accurately ascribe the chemical shifts
29 of all protons and carbons. The plots of HSQC NMR analysis confirms the expected
30 structures of both terpenes obtained predominantly by the anti-Markovnikov³⁰ addition
31 (Scheme 2). A zoom of HSQC NMR spectrum (see Figure SI-3 in Supporting Information)
32 displays additional methyne ($\delta = 39.0$ ppm) and methyl ($\delta = 19.4$ ppm) groups suggesting the
33 presence of a small amount of the Markovnikov addition product. From the integration of the
34 doublet at 1.10 ppm, this secondary structure corresponds to only 5 mol-% of the main
35 Terpene 2. Finally, the absence of additional signal of any thioester group between 170 and
36 210 ppm (see complete ¹³C NMR spectrum of Terpene 2 in Figure SI-2 of Supporting
37 Information) excludes transesterification side reaction between acid-based terpene and 3-
38 mercaptopropionic acid.³¹
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60



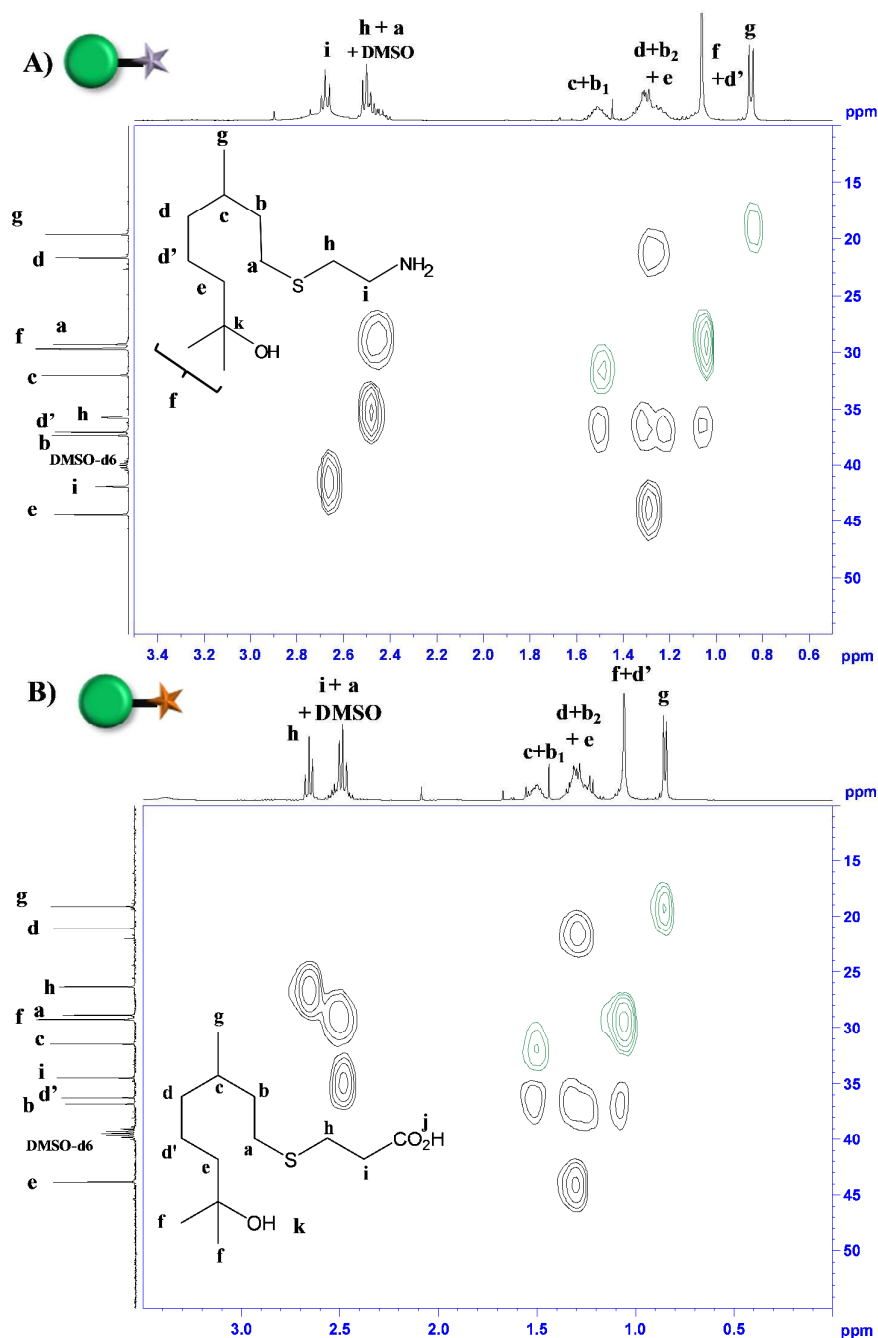


Figure 3. HSQC spectra of Terpene 1 (A) and Terpene 2 (B) in $\text{DMSO-}d_6$.

The influence of both thiol and initiator concentrations on the double bond conversion was investigated and the results are reported in Table 1. We first observed that an excess of thiol transfer agent compared to alkene function is required for a complete coupling reaction. Indeed, a stoichiometric amount of cysteamine hydrochloride versus dihydromyrcenol (entry 1 in Table 1) led to only 50 % of DHM conversion to terpene 2. While keeping an excess of

thiol versus ene groups ($[RSH]/[DHM] > 2$), even lower AIBN concentration conducted to 100 % of coupling efficiency (entries 2 – 3 of Table 1). We could note that the cysteamine hydrochloride salt was not fully soluble in DHM at the beginning of the reaction but the final product became soluble. On the other hand, 3-mercaptopropionic acid being initially soluble in DHM, the stoichiometry between thiol and ene functional group was sufficient to provide 100 % of double bond conversion (see entries 4-5 in Table 1). Note that adding cysteamine instead of cysteamine hydrochloride resulted in the absence of coupling reaction, neither in bulk nor in DMSO solvent. In most of the previous studies, either Boc-cysteamine³² or cysteamine hydrochloride³³⁻³⁶ were involved in thiol-ene chemistry. Amine functionalities must be protected or masked by hydrochloric acid because otherwise the thiol is deprotonated and thiyl radical cannot be formed.³⁷


Table 1. Thiol-ene chemistry reaction between dihydromyrcenol (DHM) terpene and functional thiols carried out at T = 80 °C in bulk.^a

Entry	R-SH	$[DHM]_0$ <i>mol.L⁻¹</i>	$[R-SH]_0$ <i>mol.L⁻¹</i>	$[AIBN]_0$ <i>mol.L⁻¹</i>	Time <i>h</i>	Conversion ^a %	Terpene
1	Cysteamine hydrochloride	5.5	5.5	5.5×10^{-1}	24	50	1
2	Cysteamine hydrochloride	5.5	16.5	5.5×10^{-1}	24	100	1
3	Cysteamine hydrochloride	5.5	11	2.7×10^{-1}	24	100	1
4	3-mercaptopropionic acid	3.6	3.6	3.6×10^{-1}	4	100	2
5	3-mercaptopropionic acid	3.6	3.6	3.6×10^{-2}	4	100	2

^a Conversion of double bond determined by ¹H NMR using the integrations of initial DHM and final terpene (see Figure 1): $\text{conversion} = [1 - (I_{g,DHM} / (I_{g,DHM} + I_{e,terpene}))] \times 100$.

Synthesis of α -telechelic terpene modified dextran. The average number of anhydroglucose units (AGU) of the initial dextran was equal to 16 according to the number average molar mass determined by aqueous size exclusion chromatography using a MALS detector ($M_n = 2600$ g/mol, $M_w/M_n = 1.46$). Dextran was functionalized at its reducing end-

group *D*-glucose residue with the reactive amino group of the Terpene **1** in the presence of sodium cyanoborohydride (**Scheme 3**).

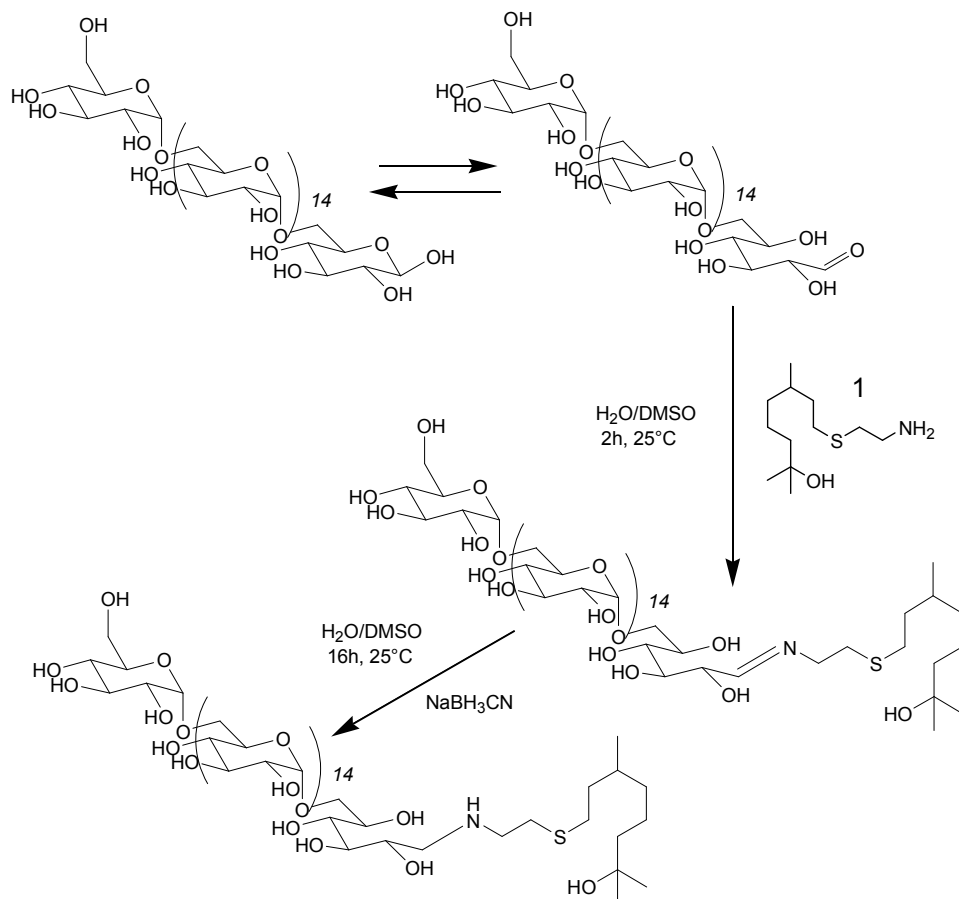

Scheme 3. Synthesis of α -telechelic modified dextran (Dext-DHM) synthesized by reductive amination of dextran with terpene **1**.

The proton NMR spectrum of terpene end-modified dextran (**Figure 4**) which was purified by several precipitations into methanol, shows the characteristic signals of terpene **1** protons. The functionalization degree of dextran chains was calculated from the ratio between the area corresponding to the signal of the 3 methylic protons of terpene **1** ($\delta_g = 0.85$ ppm) and those from the 15 anomeric protons in dextran ($\delta_a = 4.7$ ppm). A functionalization degree of 94 % proved the success of the reductive amination reaction. We should note that the absence of dextran degradation during reductive amination has been previously shown by the analysis of the molar mass of dextran before and after the reaction.³⁸ The hydrophilic lipophilic balance

(HLB) of the end-modified dextran polymer (Dext-DHM) was calculated from the simplified Griffin method proposed for non ionic surfactants ($HLB = 20 \times (\text{molar mass hydrophilic moiety}/\text{molar mass hydrophobic moiety})$).³⁹ The calculated HLB value of the synthesized Dext-DHM (HLB ~ 18.5) is close to Tween 20 non-ionic surfactants (poly(ethylene oxide) sorbitan fatty acid esters with lauric acid hydrophobic group and 20 ethylene oxide units)⁴⁰ which are known for their wide range of emulsifying properties.⁴¹⁻⁴⁵


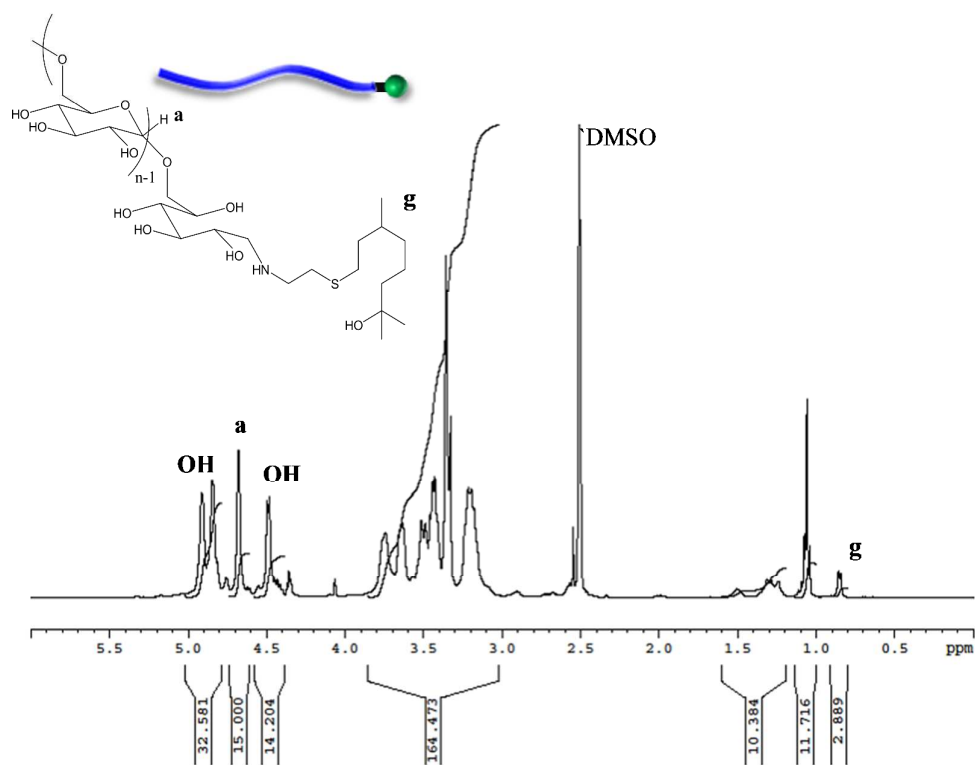



Figure 4. ^1H NMR spectrum of Dext-DHM (in $\text{DMSO-}d_6$)

Synthesis of terpene grafted dextran: hydrophobically modified dextran. The second strategy focuses on the grafting of the hydrophobic terpene group along the dextran backbone in order to tune the hydrophobic content of the amphiphilic modified dextran *via* the number of grafted terpene molecules. Terpene **2** derivatized with carboxylic acid group was covalently grafted onto the polysaccharide by esterification reaction carried out in dimethylsulfoxide at 60°C in the presence of *N,N'*-dicyclohexylcarbodiimide (**Scheme 4**).

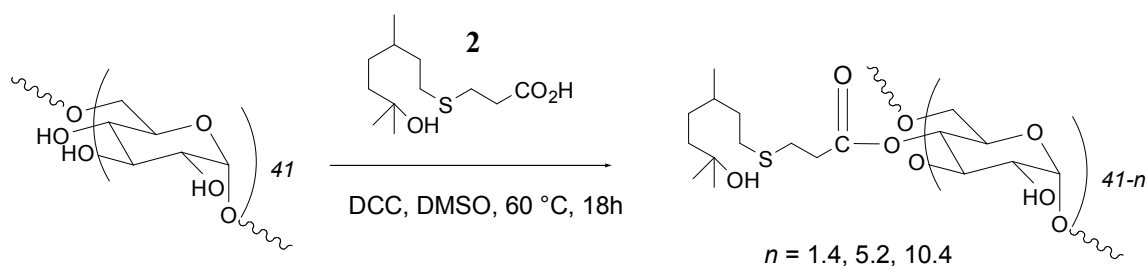

Scheme 4. Synthesis of hydrophobically modified dextran (Dext-graft-DHM) by esterification reaction between dextran and Terpene 2.

The efficient grafting of terpene 2 was evidenced by the presence of characteristic peaks of protons *f* and *g* in the NMR spectrum of the amphiphilic copolymer precipitated several times (**Figure 5**). The number of grafted DHM units per chain of dextran polymer was calculated from equation (1) using the NMR integrations of both DHM methylic protons (I_g) and dextran anomeric protons ($I_{(a+a')}$) (see Figure 5). Prior NMR analysis, the hydrophobically modified dextran was carefully precipitated three times into methanol to remove any unreacted terpene 2.

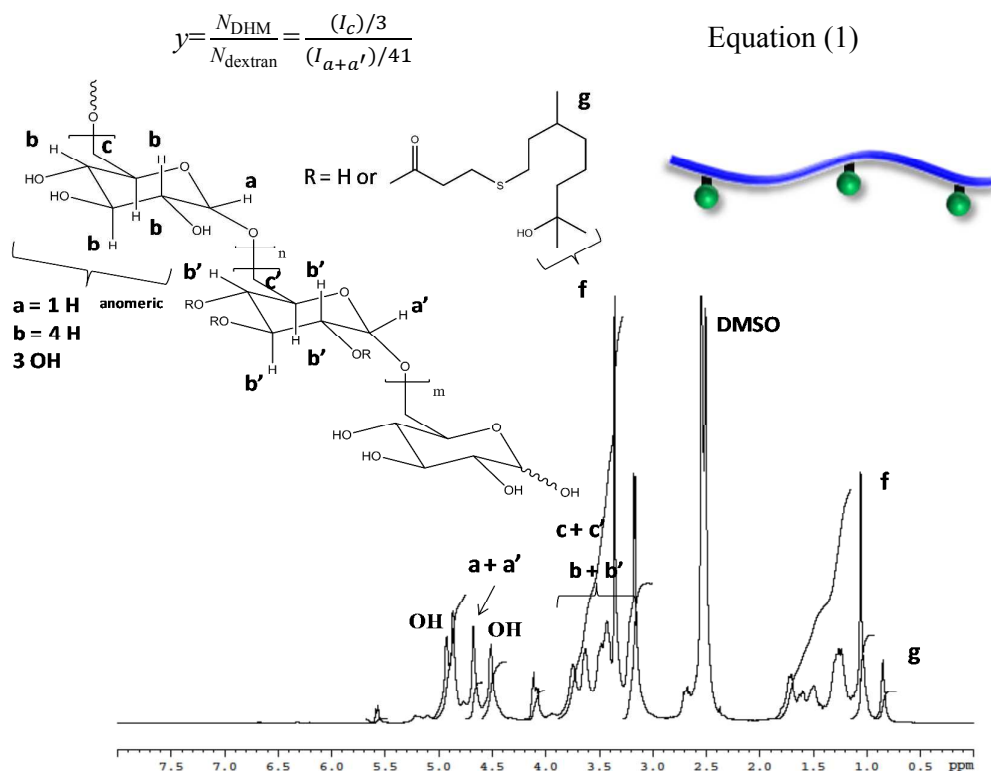

As depicted in **Table 2**, we successfully synthesized three different terpene modified dextrans exhibiting 1, 5 and 10 grafted terpene molecules per polysaccharide chain corresponding to a degree of substitution (DS), *ie.* the number of terpene functions per glucosidic unit, ranging between 2.4 and 24.4 %. By applying the simplified Griffin method,³⁹ the HLB values of these grafted dextrans ranged between 15 and 19.

Table 2. Synthesis of dextran-*graft*-DHM by esterification of dextran^a with Terpene 2 carried out at 60°C for 18 h in DMSO.

Exp	Polymer	$x = \frac{n_{\text{DHM},0}}{n_{\text{dextran},0}}$ ^b	$y = \frac{N_{\text{DHM}}}{N_{\text{dextran}}}$ ^c	DS ^d (%)
1	Dext- <i>graft</i> -DHM _{1,4}	10	1.4	3.4
2	Dext- <i>graft</i> -DHM _{5,2}	50	5.2	12.7
2	Dext- <i>graft</i> -DHM _{10,4}	100	10.4	25.4

^a Dextran 8 polymer from Serva Electrophoresis®: $M_{n,\text{dext}} = 6600 \text{ g}\cdot\text{mol}^{-1}$, $M_w/M_n = 2.2$, $N_{\text{AGU}} = 41$

^b Initial number of moles of DHM terpene over number of moles of dextran polymer chains, $x = (m_{\text{DHM},0}/FW_{\text{DHM}})/(m_{\text{dextran},0}/M_{n,\text{dext}})$

^c Average final number of DHM units per dextran polymer chain analyzed by proton NMR of the precipitated of Dext-*graft*-DHM (see Figure 5 and equation (1)).

^d Degree of substitution of the Dext-*graft*-DHM, *ie.* number of DHM functions per glucosidic unit .

Stabilization of DHM Terpene Liquid miniemulsion. It was considered of interest for cosmetic formulations to study the surface active properties of the terpene graft dextrans for emulsifying hydrophobic terpene droplets in water. The aim was to produce stable miniemulsion of dihydromyrcenol (DHM) in water stabilized by the amphiphilic biopolymers in order to facilitate the transfer of hydrophobic terpene molecules used as fragrance into aqueous formulations. For that purpose, the dihydromyrcenol was mixed with hexadecane, a








1
2
3 well-known efficient hydrophobe co-surfactant which ensures stability of the liquid
4
5 miniemulsion by suppressing the interdroplet mass diffusion, named Ostwald Ripening.^{21, 46-47}
6

7 The hydrophobic phase composed of DHM and hexadecane was mixed with a water phase
8
9 containing the terpene modified dextran prior decreasing the oil droplet size by applying shear
10
11 *via* ultrasonication (see experimental part). The stability of the liquid DHM miniemulsion (10
12
13 wt% DHM in water) was followed with time and the images of the emulsion are displayed in
14
15 **Table 3**. As expected, it was not possible to form any stable emulsion with the native
16
17 hydrophilic dextran.
18
19

20 While Dext-*graft*-DHM_{1.4} polymer containing only one terpene molecule per dextran (degree
21
22 of substitution = 2.4 %) showed poor stabilizing efficiency with evident creaming observed
23
24 after 24 hours, Dext-*graft*-DHM_{5.2} and Dext-*graft*-DHM_{10.4} polymers gave rise to stable
25
26 miniemulsions. The droplet sizes were measured by dynamic light scattering showing average
27
28 hydrodynamic diameter of the main population centered at 320 – 340 nm. A second
29
30 population of larger droplet was observed with a non-negligible intensity as light scattering is
31
32 more intense for larger colloids. Nevertheless, the liquid miniemulsion stabilized by Dext-
33
34 *graft*-DHM_{5.2} was composed of 98 % by number of the smallest 320 nm droplets. In
35
36 conclusion, the renewable terpene modified dextrans are able to act as efficient stabilizer of
37
38 direct terpene miniemulsion. The most efficient stabilizer is the dextran grafted with the
39
40 intermediate number of terpene molecules, *ie* Dext-*graft*-DHM_{5.2} (DS = 12 %), which is
41
42 slightly more efficient stabilizer than Dext-*graft*-DHM_{10.4} (DS = 24 %). This trend is
43
44 consistent with previous results reported by Durand *et al.*²² who showed a decrease of
45
46 interfacial tension between dodecane and water by increasing the degree of substitution of
47
48 hydrophobically modified dextrans from DS = 6 % to DS = 31 %. It was suggested that the
49
50 interfacial tension lowering resulted from the preferential intramolecular aggregation with
51
52
53
54
55
56
57
58
59
60

1
2
3 increasing DS, hence, reducing the availability of hydrophobic groups for adsorption at the
4
5 oil–water interface.
6
7
8

9
10 **Table 3. Results for the direct miniemulsion of DHM terpene in water.** ^a

Entry	Stabilizer	HLB ^b	t = 0	t = 24 h	<i>D_h</i> ^c nm	% by Intensity ^d	% by Number ^b
1	Native dextran	-		-	-	-	-
2	Dext- <i>graft</i> -DHM _{1,4}	19			<i>c</i>	<i>c</i>	<i>c</i>
3	Dext- <i>graft</i> -DHM _{5,2}	17			325 710	75 12	98 2
4	Dext- <i>graft</i> -DHM _{10,4}	15			340 1120	19 62	88 12

17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38 ^a Weight percent of DHM terpene versus total volume of liquid miniemulsion = 10 %; weight
39 percent of Dext-*graft*-DHM stabilizer versus terpene = 5 %; weight percent of hexadecane
40 versus terpene = 5 %.

41
42
43 ^b Hydrophilic lipophilic balance (HLB) calculated from the simplified Griffin method (HLB =
44 20 × (molar mass hydrophilic moiety/molar mass hydrophobic moiety)).³⁹

45
46
47 ^c Hydrodynamic diameter measured by dynamic light scattering 2 hours after sonication step.

48
49 ^d Non stable emulsion.

50 51 52 CONCLUSIONS

53
54
55 The quantitative thiol-ene addition of molecular thiols to dihydromyrcenol led to two types of
56 functional terpene molecules: an amino-terpene (Terpene 1) and a carboxylic acid terpene
57
58
59
60

1
2
3 (Terpene 2). Novel amphiphilic biomass-based polymers were successfully synthesized by
4
5 coupling the functional terpenes with dextran polysaccharide, either by reductive amination or
6
7 by esterification reactions. The chosen synthetic pathways offer the possibility to synthesize
8
9 either terpene end-modified dextran or terpene-grafted dextrans. When using the grafted
10
11 amphiphilic polymers as surface active macromolecular species, stable miniemulsion of
12
13 dihydromyrcenol terpene in water can be obtained with average droplet hydrodynamic
14
15 diameter of 320-340 nm. The most efficient emulsifier was the dextran hydrophobically
16
17 modified with five terpene molecules per chain, *ie* a degree of substitution of 12 %. Studies of
18
19 the stabilization efficiency for polymeric colloids are currently being in progress by
20
21 comparing the stabilization properties of the terpene grafted dextran with terpene grafted
22
23 poly(acrylic acid).
24
25
26
27
28

29 **ASSOCIATED CONTENT**

30 **Supporting Information**

31
32 ¹H and ¹³C NMR spectra of initial DHM terpene, ¹H NMR of Terpene 2 and COSY 2D-NMR
33
34 spectra of both synthesized functional terpenes are provided. This material is available free of
35
36 charge via the Internet at <http://pubs.acs.org>.
37
38
39

40 **AUTHOR INFORMATION**

41 **Corresponding Author**

42
43 * E-mail: maud.save@univ-pau.fr
44
45

46 **Author Contributions**

47
48 All authors have given approval to the final version of the manuscript.
49
50

51 **ACKNOWLEDGEMENTS**

52
53 The authors are grateful to Région Aquitaine, LVMH and DRT for financial support. The
54
55 authors thank Dr. Julien Bernard, Agnès Crepet from IMP@INSA Lyon for aqueous SEC
56
57
58
59
60

analysis of dextran and Abdel Khoukh (IPREM-EPCP) for NMR analyses. ANR-10-EQPX-16 XYLOFOREST funding is acknowledged.

REFERENCES

- (1) Stevens, C. V.; Meriggi, A.; Booten, K. *Biomacromolecules* **2001**, *2*, 1-16.
- (2) Lahaye, M.; Robic, A. *Biomacromolecules* **2007**, *8*, 1765-1774.
- (3) Rose, M.; Palkovits, R. *Macromol. Rapid Commun.* **2011**, *32*, 1299-1311.
- (4) Figueiredo, J. A.; Ismael, M. I.; Anjo, C. M. S.; Duarte, A. P., Cellulose and Derivatives from Wood and Fibers as Renewable Sources of Raw-Materials. In *Carbohydrates in Sustainable Development I: Renewable Resources for Chemistry and Biotechnology*, Rauter, A. P.; Vogel, P.; Queneau, Y., Eds. Springer-Verlag Berlin: Berlin, 2010; Vol. 294, pp 117-128.
- (5) Wilbon, P. A.; Chu, F. X.; Tang, C. B. *Macromol. Rapid Commun.* **2013**, *34*, 8-37.
- (6) Yao, K. J.; Tang, C. B. *Macromolecules* **2013**, *46*, 1689-1712.
- (7) Zhao, J. P.; Schlaad, H., Synthesis of Terpene-Based Polymers. In *Bio-Synthetic Polymer Conjugates*, Schlaad, H., Ed. Springer-Verlag Berlin: Berlin, 2013; Vol. 253, pp 151-190.
- (8) Sharma, S.; Srivastava, A. K. *J. Macromol. Sci., Part A: Pure Appl.Chem.* **2003**, *A40*, 593-603.
- (9) Sharma, S.; Srivastava, A. K. *Polym.-Plast. Technol. Eng.* **2003**, *42*, 485-502.
- (10) Sharma, S.; Srivastava, A. K. *Eur. Polym. J.* **2004**, *40*, 2235-2240.
- (11) Sharma, S.; Srivastava, A. K. *J. Appl. Polym. Sci.* **2004**, *91*, 2343-2347.
- (12) Firdaus, M.; de Espinosa, L. M.; Meier, M. A. R. *Macromolecules* **2011**, *44*, 7253-7262.
- (13) Zhao, J. P.; Jeromenok, J.; Weber, J.; Schlaad, H. *Macromol. Biosci.* **2012**, *12*, 1272-1278.
- (14) Zhao, J. P.; Schlaad, H.; Weidner, S.; Antonietti, M. *Polym. Chem.* **2012**, *3*, 1763-1768.
- (15) Singh, V.; Kumar, P.; Sanghi, R. *Prog. Polym. Sci.* **2012**, *37*, 340-364.
- (16) Tizzotti, M.; Charlot, A.; Fleury, E.; Stenzel, M.; Bernard, J. *Macromol. Rapid Commun.* **2010**, *31*, 1751-1772.
- (17) Ydens, I.; Rutot, D.; Degee, P.; Six, J. L.; Dellacherie, E.; Dubois, P. *Macromolecules* **2000**, *33*, 6713-6721.
- (18) Wang, C. Q.; Li, G. T.; Tao, S. Y.; Guo, R. R.; Yan, Z. *Carbohydr. Polym.* **2006**, *64*, 466-472.
- (19) Habibi, Y.; Goffin, A. L.; Schiltz, N.; Duquesne, E.; Dubois, P.; Dufresne, A. *J. Mater. Chem.* **2008**, *18*, 5002-5010.
- (20) Qiu, X. Y.; Wang, C. Q.; Shen, J. A.; Jiang, M. W. *Carbohydr. Polym.* **2011**, *83*, 1723-1729.
- (21) Durand, A.; Marie, E.; Rotureau, E.; Leonard, M.; Dellacherie, E. *Langmuir* **2004**, *20*, 6956-6963.
- (22) Durand, A.; Dellacherie, E. *Colloid Polym. Sci.* **2006**, *284*, 536-545.
- (23) Durand, A. *Colloid Polym. Sci.* **2008**, *286*, 1505-1510.
- (24) Obiols-Rabasa, M.; Ramos, J.; Forcada, J.; Esquena, J.; Solans, C.; Levecke, B.; Booten, K.; Tadros, T. F. *Langmuir* **2010**, *26*, 7717-7724.
- (25) Kaewprapan, K.; Baros, F.; Marie, E.; Inprakhon, P.; Durand, A. *Carbohydr. Polym.* **2012**, *88*, 313-320.
- (26) Claudino, M.; Jonsson, M.; Johansson, M. *RSC Adv.* **2013**, *3*, 11021-11034.

- 1
2
3 (27) Hoyle, C. E.; Bowman, C. N. *Angew. Chem., Int. Ed.* **2010**, *49*, 1540-1573.
4 (28) Hoyle, C. E.; Lee, T. Y.; Roper, T. *J. Polym. Sci., Part A-1: Polym. Chem.* **2004**, *42*,
5 5301-5338.
6 (29) Cramer, N. B.; Reddy, S. K.; O'Brien, A. K.; Bowman, C. N. *Macromolecules* **2003**,
7 *36*, 7964-7969.
8 (30) Posner, T. *Ber. Dtsch. Chem. Ges.* **1905**, *38*, 646-657.
9 (31) Jailliet, F.; Desroches, M.; Auvergne, R.; Boutevin, B.; Caillol, S. *Eur. J. Lipid Sci.*
10 *Technol.* **2013**, *115*, 698-708.
11 (32) Silverstein, J. S.; Casey, B. J.; Natoli, M. E.; Dair, B. J.; Kofinas, P. *Macromolecules*
12 **2012**, *45*, 3161-3167.
13 (33) Franz, N.; Menin, L.; Klok, H. A. *Org. Biomol. Chem.* **2009**, *7*, 5207-5218.
14 (34) Jia, Z. F.; Liu, J. Q.; Davis, T. P.; Bulmus, V. *Polymer* **2009**, *50*, 5928-5932.
15 (35) Stemmelen, M.; Pessel, F.; Lapinte, V.; Caillol, S.; Habas, J. P.; Robin, J. J. *J. Polym.*
16 *Sci., Part A-1: Polym. Chem.* **2011**, *49*, 2434-2444.
17 (36) Auvergne, R.; Desroches, M.; Clerc, S.; Carlotti, S.; Caillol, S.; Boutevin, B. *React.*
18 *Funct. Polym.* **2012**, *72*, 393-401.
19 (37) Krannig, K. S.; Schlaad, H. *J. Am. Chem. Soc.* **2012**, *134*, 18542-18545.
20 (38) Jeong, Y. I.; Kim, D. G.; Kang, D. H. *Journal of Chemistry* **2013**, DOI
21 10.1155/2013/414185.
22 (39) Griffin, W. C. *Cosmet. Chem. J. Soc.* **1949**, *1*, 311-326.
23 (40) Pasquali, R. C.; Taurozzi, M. P.; Bregni, C. *Int. J. Pharm. (Amsterdam, Neth.)* **2008**,
24 *356*, 44-51.
25 (41) Eskandani, M.; Hamishehkar, H.; Dolatabadi, J. E. N. *DNA and Cell Biology* **2013**, *32*,
26 498-503.
27 (42) Xin, X.; Zhang, H. X.; Xu, G. Y.; Tan, Y. B.; Zhang, J.; Lv, X. *Colloids Surf., A* **2013**,
28 *418*, 60-67.
29 (43) Losada-Barreiro, S.; Sanchez-Paz, V.; Bravo-Diaz, C. *J. Colloid Interface Sci.* **2013**,
30 *389*, 1-9.
31 (44) Qian, C.; Decker, E. A.; Xiao, H.; McClements, D. J. *J. Am. Oil Chem. Soc.* **2012**, *89*,
32 17-28.
33 (45) Gulseren, I.; Coupland, J. N. *J. Am. Oil Chem. Soc.* **2007**, *84*, 621-629.
34 (46) Mishchuk, N. A.; Verbich, S. V.; Dukhin, S. S.; Holt, O.; Sjoblom, J. *J. Dispersion*
35 *Sci. Technol.* **1997**, *18*, 517-537.
36 (47) Landfester, K. *Macromol. Rapid Commun.* **2001**, *22*, 896-936.
37
38
39
40
41
42
43
44

Table of Contents Graphic (TOC)

